

Investigation of the influence of the molecular weight of polyethyleneglycols on the optical properties and dispersed characteristics of sols of Au nanoparticles used in medicine

Abstract

In this work, the synthesis of Au nanoparticles stabilized with polyethyleneglycols with different molecular weights from 200 to 8000 Da was carried out. The synthesis was carried out by the method of chemical reduction in an aqueous medium using sodium citrate as a reducing agent. The dependence of the optical properties on the concentration and molar mass of polyethyleneglycol was studied in the obtained samples of Au nanoparticles. The absorption spectra were recorded using an SF-56 optical spectrometer. The studies were carried out in the visible range of the spectrum from 400 to 800 nm. It was found that the type of spectrum, the position of the surface plasmon resonance band and the optical density of the samples of Au nanoparticles stabilized with PEG-8000 with a concentration of 10 and 20% did not undergo significant changes during storage, which characterizes the high aggregate stability of these sols. The dispersed characteristics of these samples of sols of Au nanoparticles were also studied. The studies were carried out using photon-correlation spectroscopy by the method of dynamic light scattering. It is established that an increase in the concentration of the stabilizer leads to an increase in the average hydrodynamic radius of the particles. This fact is associated with an increase in the thickness of the stabilizer layer and with the "stitching" of the polymer layer of Au nanoparticles with the formation of aggregates. Thus, the best result was found in PEG-8000 samples with concentrations of 10 and 20%, since the type of spectrum, the position of the surface plasmon resonance band and the optical density did not undergo significant changes. Based on the data obtained, it can be concluded that the best stabilizer for Au nanoparticles obtained by the citrate method is PEG-8000 with a concentration of at least 10 %. It is important to note that with an increase in the concentration of the stabilizer, the average hydrodynamic radius of the particles increases. This fact is associated with an increase in the thickness of the stabilizer layer and with the "stitching" of Au nanoparticles.

Key words: Au nanoparticles, polyethyleneglycol, spectrophotometry, plasmon resonance.

Introduction

Recently, Au nanoparticles have found wide practical application in various fields of science and technology. Au nanoparticles are used in optics to enhance polar-sensitive optical processes (1,2), in biomedicine, as a means of targeted drug delivery (3–7), as a means for the treatment and diagnosis of bacterial infections (8–10), in biosensorics for the detection of oncological diseases, where it acts as an immobilizer of the probe surface (11–13), as heterogeneous catalysts (14–16), in photoelectronics (17).

There are many methods that allow synthesizing Au nanoparticles of various sizes and shapes. The synthesis of Au nanoparticles with a controlled size using condensation in an inert gas is known (18), short Au nanorods (19), monodisperse Au nanoparticles with a tunable size and frequency of surface plasmon resonance (20). Variants of the Turkevich – Frans synthesis method have been frequently used in recent years (21–26). A "green" method for obtaining Au nanoparticles is known, proposed by Raveendran P. (27). According to Liu Y-C. (28), a method for obtaining Au nanoparticles by the electrochemical method is presented. Huang X. (29) has obtained anisotropic Au nanostructures by photochemical reduction of $HAuCl_4$.

50 The issue of stabilization of nanoparticles, in particular Au nanoparticles, is
51 relevant (30–37). In work Zhao W. (30), the stabilization of Au nanoparticles in
52 aqueous solutions by mononucleotides is considered. It is known that
53 polyethyleneglycol dendrimers are used to stabilize Au nanoparticles (38,39). Chitosan
54 (40–42) and albumin (43) can be used as a stabilizer. According Yasmin A. (44), a
55 method for stabilizing Au nanoparticles with pink-blueberry hibiscus extract was
56 described, the presence of Au nanoparticles with a diameter of 16 to 30 nm was
57 confirmed using optical spectroscopy and transmission electron microscopy. Jia X. (45)
58 reports on the study of stabilized Au nanoparticles from chlorogenic acid using lentinan.

59 As a result of the promising application of this material, the aim of this work is to
60 synthesize and optimize the method for obtaining Au nanoparticles, as well as to study
61 the optical properties and stability of the obtained samples.

62 **Materials and Methods**


63 In this work, sols of Au nanoparticles were synthesized by the citrate method.
64 Au-Hydrochloric acid (StavReaChem, Stavropol, Russian Federation) was used as a
65 precursor, sodium citrate (StavReaChem, Stavropol, Russian Federation) was used as a
66 reducing agent. Polyethyleneglycol (PEG) (LDChem, Dzerzhinsk, Russian Federation)
67 with different molecular weights was used to stabilize Au nanoparticles. The
68 concentration of the stabilizer was varied from 1 to 20 wt.%.

69 The obtained samples of sols of Au nanoparticles stabilized by PEG were studied
70 by the method of dynamic light scattering at the Photocor-Complex installation (Antek-
71 97 LLC, Russian Federation) (46). Computer processing of the results was carried out
72 using the DynaLS computer software.

73 The optical characteristics of sols of Au nanoparticles were studied by optical
74 spectroscopy on the SF-56 spectrophotometer (OKB-Specter, Saints Petersburg,
75 Russian Federation). The studies were carried out in the visible range of the spectrum
76 from 400 to 800 nm (47).


77 **Results and Discussion**

78 At the first stage, sols of Au nanoparticles stabilized with polyethylene glycols
79 with a molecular weight from 200 to 8000 Da were studied by spectrophotometry. The
80 results are shown in Figures 1-5.
81
82
83

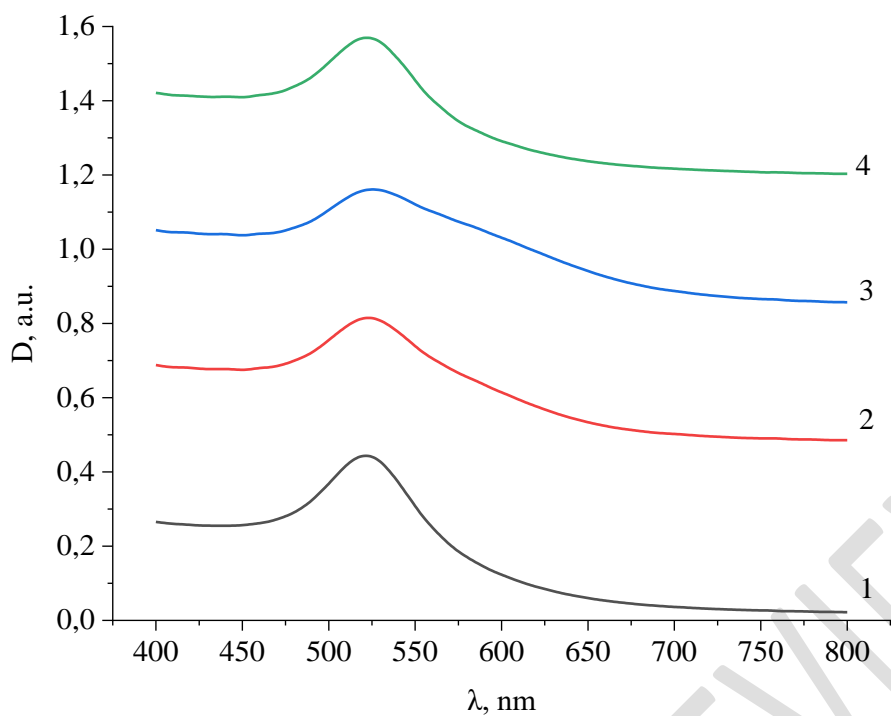

1 – 1 mac. %; 2 – 5 %; 3 – 10 %; 4 – 20 %

Figure 1. Absorption spectrum of Au nanoparticles stabilized by PEG-200

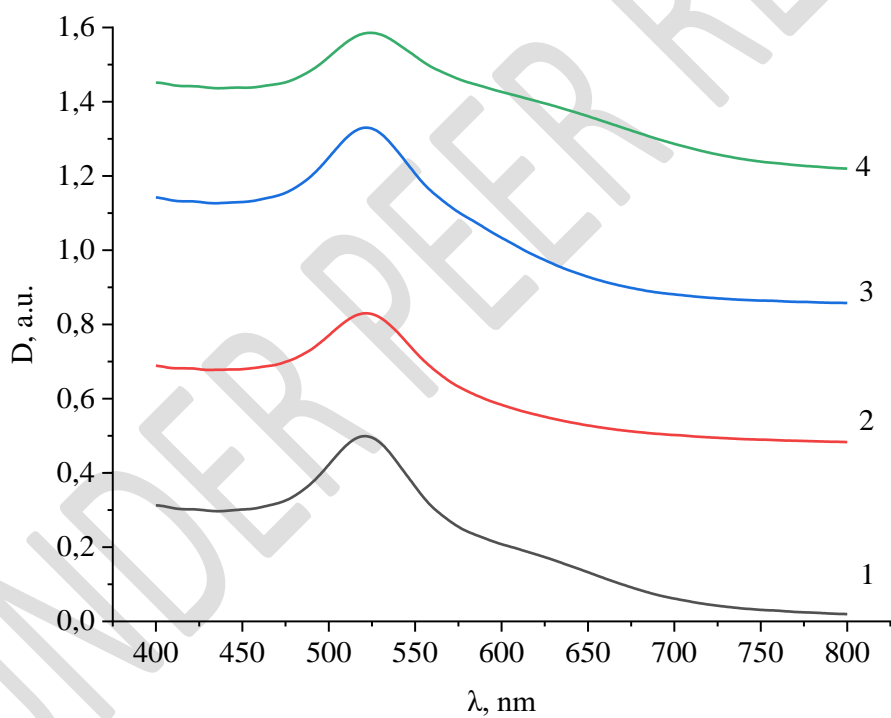


1 – 1 %; 2 – 5 %; 3 – 10 %; 4 – 20 %

Figure 2. Absorption spectrum of Au nanoparticles stabilized by PEG-400


84
85
86
87

88
89
90
91
92

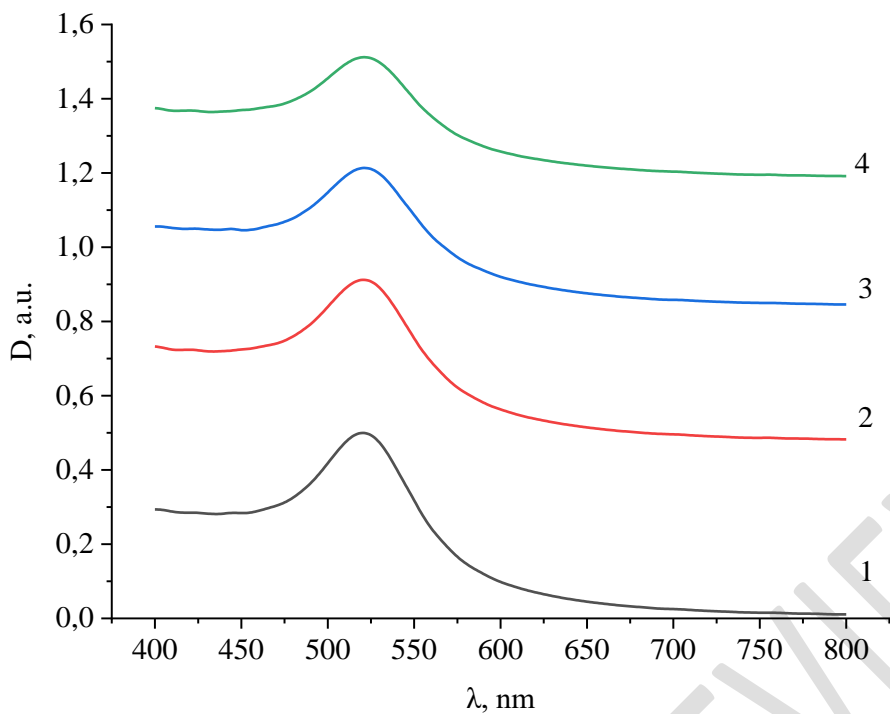

1 – 1 %; 2 – 5 %; 3 – 10 %; 4 – 20 %

Figure 3. Absorption spectrum of Au nanoparticles stabilized by PEG-1500

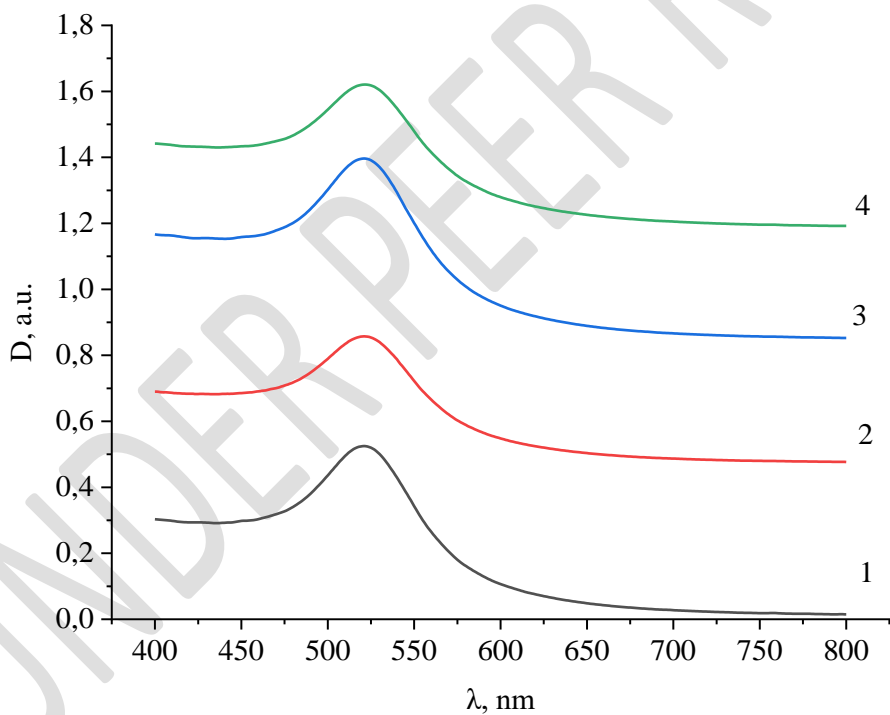


1 – 1 %; 2 – 5 %; 3 – 10 %; 4 – 20 %

Figure 4. Absorption spectrum of Au nanoparticles stabilized by PEG-4000

93
94
95
96
97

98
99
100
101
102

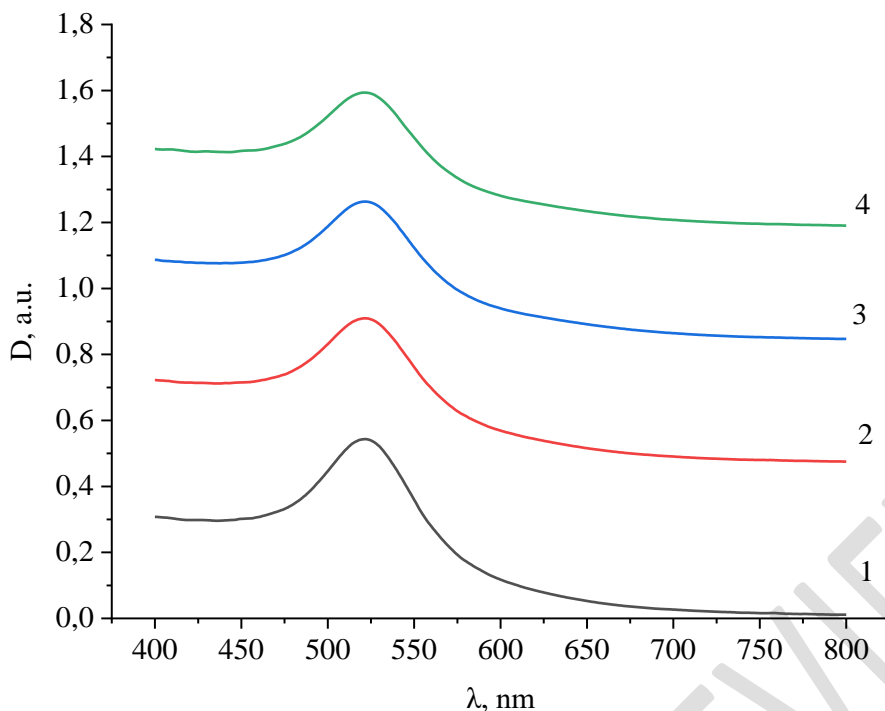

1 – 1 %; 2 – 5 %; 3 – 10 %; 4 – 20 %


Figure 5. Absorption spectrum of Au nanoparticles stabilized by PEG-6000

103
104
105
106

107 As a result of the analysis of the obtained absorption spectra, it can be concluded
108 that Au nanoparticles are present in all samples stabilized with polyethyleneglycol, as
109 evidenced by the presence of bands at 520 – 526 nm in the spectrum, which correspond
110 to the surface plasmon resonance of Au nanoparticles.

111 Then the sols of Au nanoparticles were re-examined a month later. The obtained
112 absorption spectra are shown in Figures 6-10. Table 1 shows a comparison of the
113 spectra obtained immediately after synthesis and the spectra obtained a month after
114 synthesis.


115

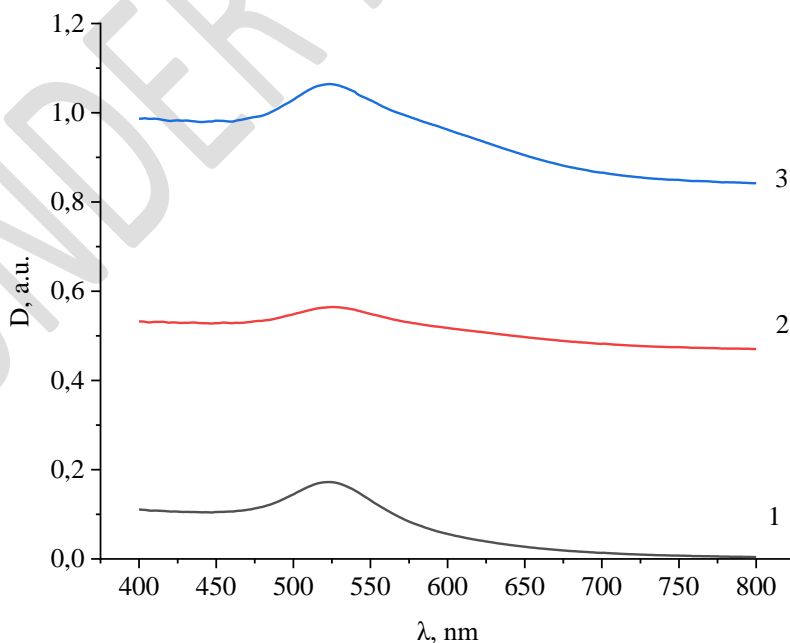

1 – 1 %; 2 – 5 %; 3 – 10 %


Figure 6. Absorption spectrum of Au nanoparticles stabilized with PEG-200 after 30 days of storage at room temperature

116
117
118
119

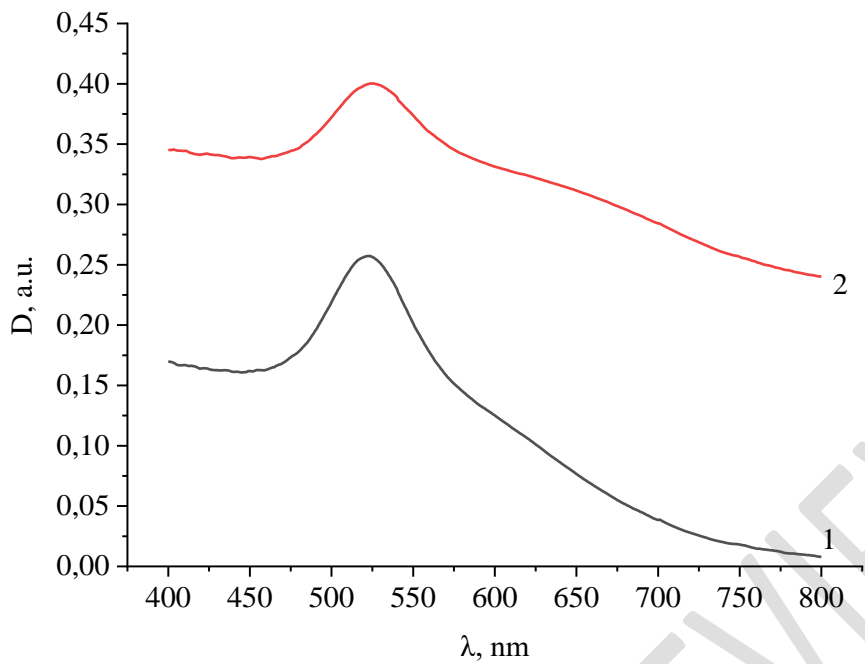


120
121
122
123
124

1 – 10 %; 2 – 20 %
Figure 7. Absorption spectrum of Au nanoparticles stabilized with PEG-400 after 30 days of storage at room temperature

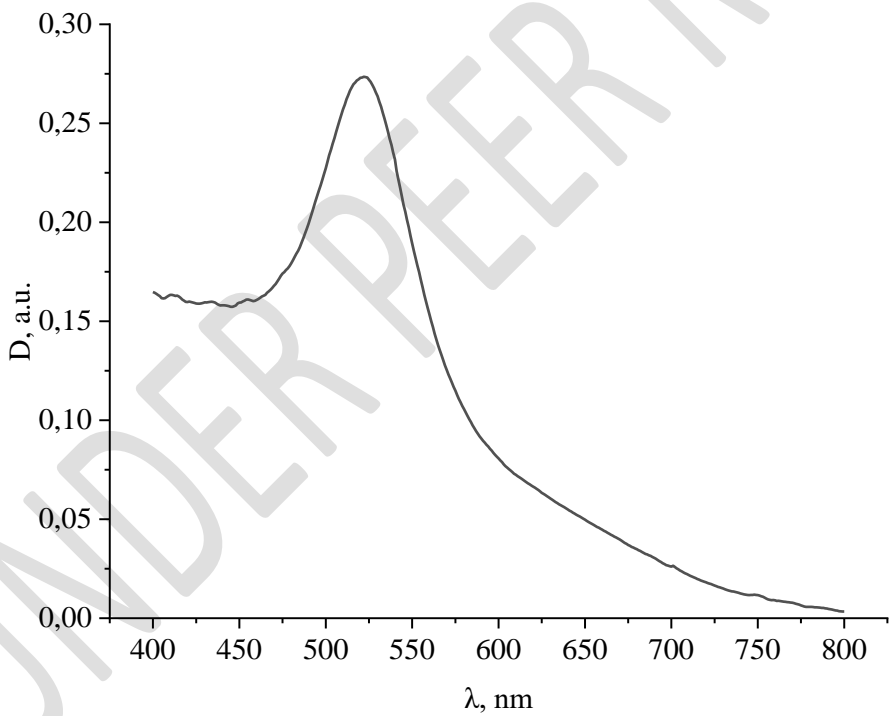


125
126
127
128
129

Figure 8. Absorption spectrum of Au nanoparticles stabilized with PEG-1500 after 30 days of storage at room temperature (20% content)

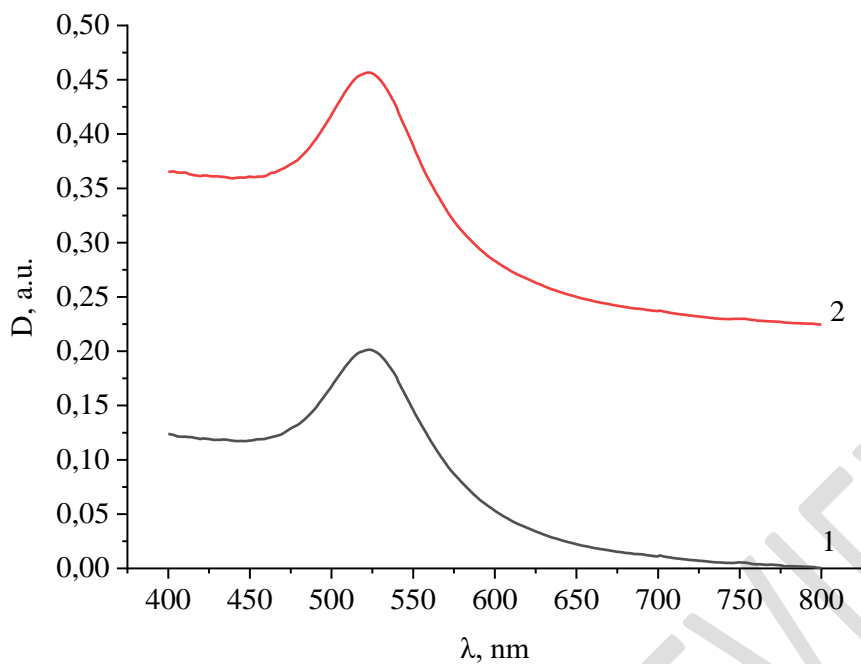

130
131
132
133
134
135

1 – 10 %; 2 – 20 %
Figure 9. Absorption spectrum of Au nanoparticles stabilized with PEG-4000 after 30 days of storage at room temperature

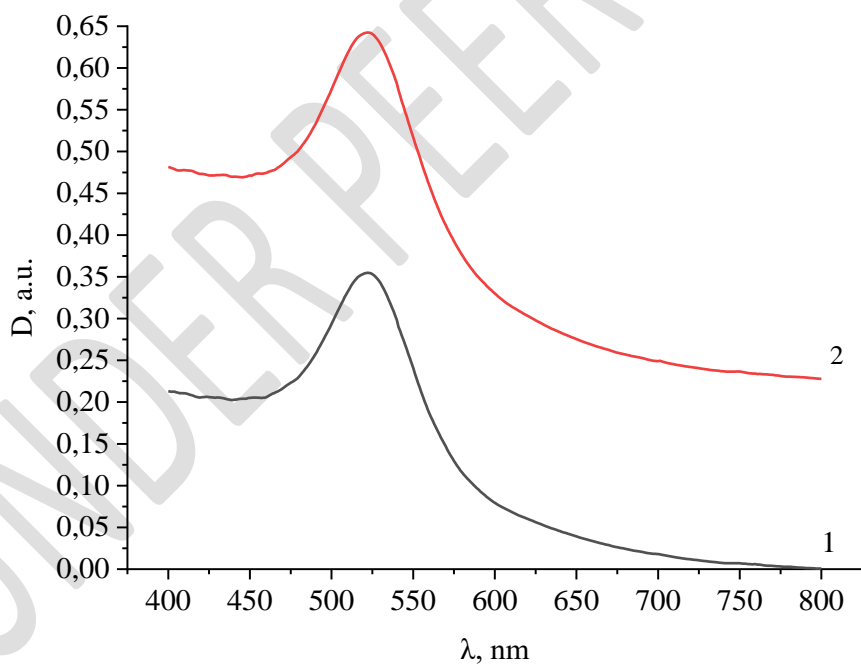

136
137
138
139
140
141
142
143
144
145

1 – 10 %; 2 – 20 %
Figure 10. Absorption spectrum of Au nanoparticles stabilized with PEG-6000 after 30 days of storage at room temperature

Table 1. Optical properties of Au nanoparticles stabilized by PEG with different molecular weight and concentration

PEG brand	PEG concentration, %	The position of the band at the initial time, nm	The position of the peak λ in a month, nm	D, a u. at the initial moment of time	D, a u. in a month, nm
PEG 200	1	522	470	0,4433	0,1099
	5	523	524	0,3473	0,0971
	10	526	524	0,3259	0,2292
	20	522	0	0,3932	0
PEG 400	1	521	0	0,4991	0
	5	522	0	0,3625	0
	10	522	522	0,4951	0,2573
	20	524	524	0,4093	0,1755
PEG 1500	1	520	0	0,499732	0
	5	521	0	0,4447	0
	10	521	0	0,3784	0
	20	521	522	0,3355	0,2735
PEG 4000	1	521	0	0,5248	0
	5	521	0	0,3898	0
	10	521	523	0,5614	0,2014
	20	522	522	0,4443	0,2318
PEG 8000	1	522	0	0,5433	0
	5	522	0	0,4418	0
	10	522	522	0,4283	0,3548
	20	521	522	0,4173	0,4176

As a result of the analysis of the obtained data, it was revealed that the molecular weight and concentration of polyethyleneglycol significantly affect the stability of sols of Au nanoparticles. The second band is observed in the PEG-400 sample with concentrations of 1 and 20%, which indicates the content of an anisotropic form in the samples. In samples stabilized with PEG-200 with a concentration of 20 %, PEG-400 (1 %, 5 %), PEG-1500 (1 %, 5 %, 10 %), PEG-4000 (1 %, 5 %) and PEG-8000 (1 %, 5 %), a significant decrease in the intensity of the surface plasmon resonance band was found during repeated examination, which indicates the formation of large agglomerates.

The best result was found in PEG-8000 samples with concentrations of 10 and 20%, since the type of spectrum, the position of the surface plasmon resonance band and the optical density did not undergo significant changes. Based on the data obtained, it can be concluded that the best stabilizer for Au nanoparticles obtained by the citrate method is PEG-8000 with a concentration of at least 10 %.

Then, the average hydrodynamic radius of the sols of Au nanoparticles, stabilized polyethyleneglycols with a molecular weight of 8000 Da, was determined by the method of dynamic light scattering. The results are shown in Figure 11 and in Table 2.

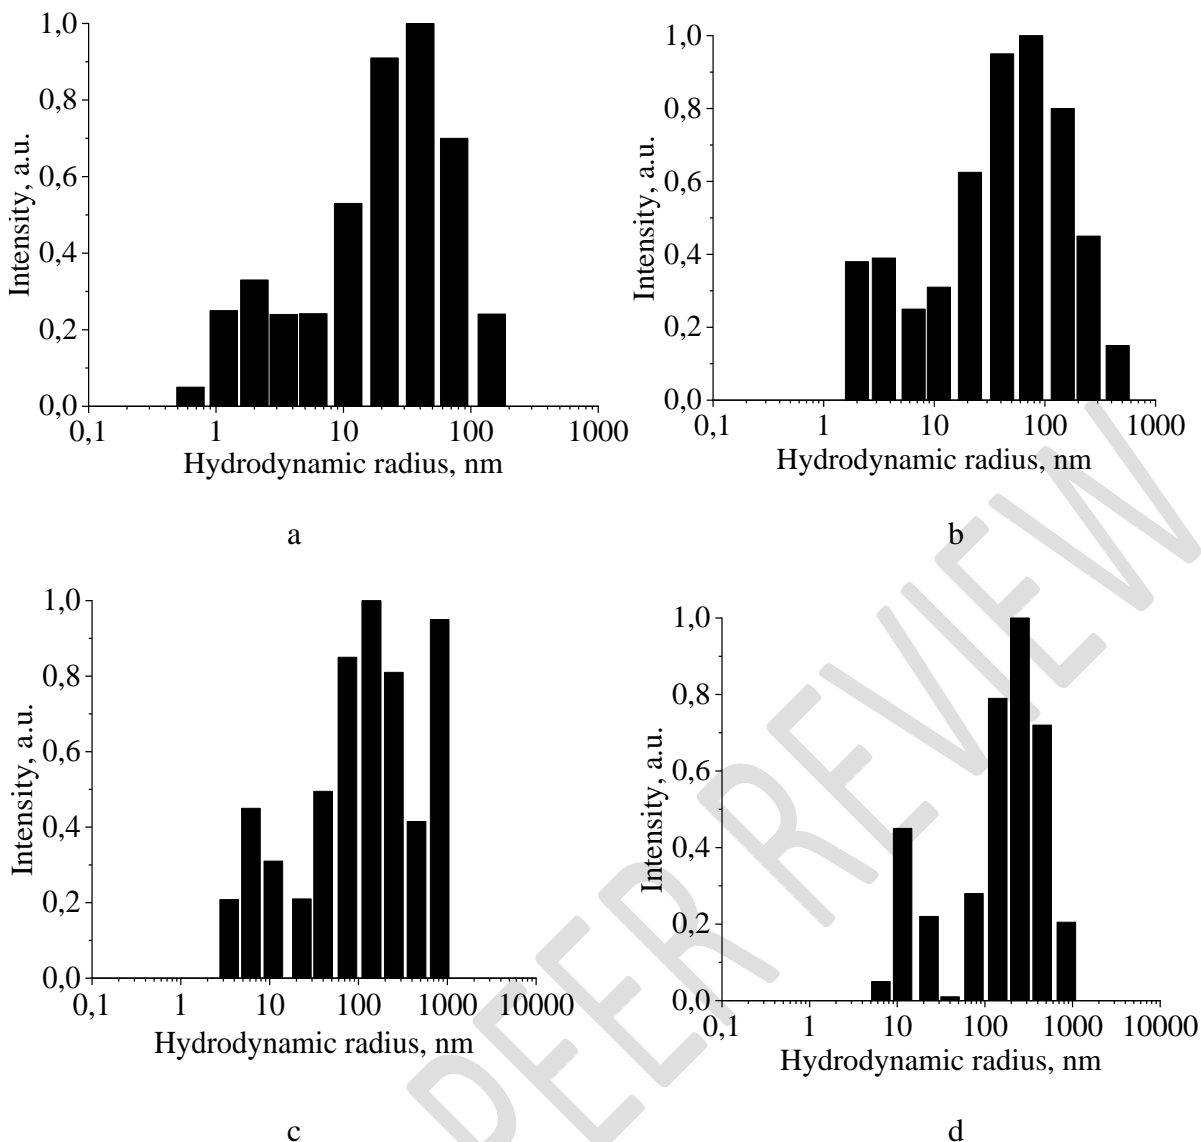


Figure 11. Histograms of the distribution of hydrodynamic radii of Au nanoparticles stabilized with PEG 8000: a-1%; b-5%; c-10%;d-20%

Table 2. Results of the study of Au nanoparticle samples by dynamic light scattering

	PEG 8000 1%	PEG 8000 5%	PEG 8000 10%	PEG 8000 20%
1 st fraction	5 HM	7 HM	10 HM	13 HM
2 nd fraction	75 HM	90 HM	120 HM	200 HM

As a result of the analysis of the data obtained by the method of dynamic light scattering, it was found that in each sample of sols of Au nanoparticles stabilized by PEG-8000, there are 2 fractions: 1 fraction - from 5 to 13 nm, 2 fraction - from 75 to 200 nm. It is important to note that with an increase in the concentration of the stabilizer, the average hydrodynamic radius of the particles increases. This fact is associated with an increase in the thickness of the stabilizer layer and with the "stitching" of Au nanoparticles.

Conclusion

As a result of this work, gold nanoparticles stabilized with PEG of various grades were obtained. The obtained samples were studied by spectrophotometry and photon

188 correlation spectroscopy. Analysis of the samples showed that the molecular weight and
189 concentration of polyethylene glycol significantly affect the stability of Au nanoparticle
190 salts. The second band is observed in the PEG-400 sample with concentrations of 1 and
191 20%, which indicates the content of an anisotropic form in the samples. In samples
192 stabilized with PEG-200 with a concentration of 20%, PEG-400 (1%, 5%), PEG-1500
193 (1%, 5%, 10%), PEG-4000 (1%, 5%) and PEG-8000 (1%, 5%), repeated examination
194 revealed a significant decrease in the intensity of the surface plasmon resonance range,
195 which indicates the formation of large agglomerates.

196 The results of the study of dynamic light scattering showed that in each sample of
197 Au nanoparticle salts stabilized with PEG-8000, there are 2 fractions: 1 fraction - from 5
198 to 13 nm, 2 fractions - from 75 to 200 nm.

199 Thus, we can conclude that the best result was found in PEG-8000 samples with
200 concentrations of 10 and 20%, since the type of spectrum, the position of the surface
201 plasmon resonance band and the optical density did not undergo significant changes.
202 Based on the data obtained, it can be concluded that the best stabilizer for Au
203 nanoparticles obtained by the citrate method is PEG-8000 with a concentration of at
204 least 10 %. It is important to note that with an increase in the concentration of the
205 stabilizer, the average hydrodynamic radius of the particles increases. This fact is
206 associated with an increase in the thickness of the stabilizer layer and with the
207 "stitching" of Au nanoparticles.

208 209 **Acknowledgment**

210 The work was carried out using the equipment of the Center for Collective Use of North-Caucasus
211 Federal University with financial support from the Ministry of Science and Higher Education of
212 Russian Federation, unique project identifier RF ---- 2296.61321X0029 (agreement no. 075-15-2021-
213 687).

214 215 **COMPETING INTERESTS DISCLAIMER:**

216
217 Authors have declared that no competing interests exist. The products used for this research are
218 commonly and predominantly use products in our area of research and country. There is absolutely
219 no conflict of interest between the authors and producers of the products because we do not intend to
220 use these products as an avenue for any litigation but for the advancement of knowledge. Also, the
221 research was not funded by the producing company rather it was funded by personal efforts of the
222 authors.

223 224 225 226 **References**

- 227 1. Bigall NC, Eychmüller A. Synthesis of noble metal nanoparticles and their non-ordered
228 superstructures. *Philos Trans R Soc A Math Phys Eng Sci* [Internet]. 2010 Mar
229 28;368(1915):1385–404. Available from:
230 <https://royalsocietypublishing.org/doi/10.1098/rsta.2009.0274>
- 231 2. Favi PM, Gao M, Johana Sepúlveda Arango L, Ospina SP, Morales M, Pavon JJ, et al. Shape
232 and surface effects on the cytotoxicity of nanoparticles: Gold nanospheres versus gold
233 nanostars. *J Biomed Mater Res Part A* [Internet]. 2015 Nov;103(11):3449–62. Available from:
234 <https://onlinelibrary.wiley.com/doi/10.1002/jbm.a.35491>
- 235 3. Kumar D, Saini N, Jain N, Sareen R, Pandit V. Gold nanoparticles: an era in
236 bionanotechnology. *Expert Opin Drug Deliv* [Internet]. 2013 Mar 7;10(3):397–409. Available
237 from: <http://www.tandfonline.com/doi/full/10.1517/17425247.2013.749854>

- 238 4. Khan A, Rashid R, Murtaza G, Zahra A. Gold Nanoparticles: Synthesis and Applications in
239 Drug Delivery. *Trop J Pharm Res* [Internet]. 2014 Sep 18;13(7):1169. Available from:
240 <http://www.ajol.info/index.php/tjpr/article/view/145974>
- 241 5. GHOSH P, HAN G, DE M, KIM C, ROTELLO V. Gold nanoparticles in delivery
242 applications☆. *Adv Drug Deliv Rev* [Internet]. 2008 Aug 17;60(11):1307–15. Available from:
243 <https://linkinghub.elsevier.com/retrieve/pii/S0169409X08000999>
- 244 6. Tedesco S, Doyle H, Redmond G, Sheehan D. Gold nanoparticles and oxidative stress in
245 *Mytilus edulis*. *Mar Environ Res* [Internet]. 2008 Jul;66(1):131–3. Available from:
246 <https://linkinghub.elsevier.com/retrieve/pii/S0141113608000494>
- 247 7. Gupta A, Moyano DF, Parnsubsakul A, Papadopoulos A, Wang L-S, Landis RF, et al.
248 Ultrastable and Biofunctionalizable Gold Nanoparticles. *ACS Appl Mater Interfaces* [Internet].
249 2016 Jun 8;8(22):14096–101. Available from: <https://pubs.acs.org/doi/10.1021/acsami.6b02548>
- 250 8. Pissuwan D, Cortie CH, Valenzuela SM, Cortie MB. Functionalised gold nanoparticles for
251 controlling pathogenic bacteria. *Trends Biotechnol* [Internet]. 2010 Apr;28(4):207–13.
252 Available from: <https://linkinghub.elsevier.com/retrieve/pii/S0167779909002364>
- 253 9. Wilson R. The use of gold nanoparticles in diagnostics and detection. *Chem Soc Rev* [Internet].
254 2008;37(9):2028. Available from: <http://xlink.rsc.org/?DOI=b712179m>
- 255 10. Nagdalian AA, Rzhepakovsky I V., Siddiqui SA, Piskov SI, Oboturova NP, Timchenko LD, et
256 al. Analysis of the content of mechanically separated poultry meat in sausage using computing
257 microtomography. *J Food Compos Anal*. 2021;
- 258 11. Ensafi AA, Taei M, Rahmani HR, Khayamian T. Sensitive DNA impedance biosensor for
259 detection of cancer, chronic lymphocytic leukemia, based on gold nanoparticles/gold modified
260 electrode. *Electrochim Acta* [Internet]. 2011 Oct;56(24):8176–83. Available from:
261 <https://linkinghub.elsevier.com/retrieve/pii/S0013468611008747>
- 262 12. Saha K, Agasti SS, Kim C, Li X, Rotello VM. Gold Nanoparticles in Chemical and Biological
263 Sensing. *Chem Rev* [Internet]. 2012 May 9;112(5):2739–79. Available from:
264 <https://pubs.acs.org/doi/10.1021/cr2001178>
- 265 13. Qian X, Tan S, Li Z, Qu Q, Li L, Yang L. A robust host-guest interaction controlled probe
266 immobilization strategy for the ultrasensitive detection of HBV DNA using hollow HP5-
267 Au/CoS nanobox as biosensing platform. *Biosens Bioelectron*. 2020 Apr 1;153:112051. doi:
268 10.1016/j.bios.2020.112051.
- 269 14. Sardar R, Funston AM, Mulvaney P, Murray RW. Gold Nanoparticles: Past, Present, and
270 Future. *Langmuir* [Internet]. 2009 Dec 15;25(24):13840–51. Available from:
271 <https://pubs.acs.org/doi/10.1021/la9019475>
- 272 15. Sun Y, Xia Y. Shape-Controlled Synthesis of Gold and Silver Nanoparticles. *ChemInform*
273 [Internet]. 2003 Mar 11;34(10). Available from:
274 <https://onlinelibrary.wiley.com/doi/10.1002/chin.200310226>
- 275 16. Sankar M, He Q, Engel RV, Sainna MA, Logsdail AJ, Roldan A, Willock DJ, Agarwal N, Kiely
276 CJ, Hutchings GJ. Role of the Support in Gold-Containing Nanoparticles as Heterogeneous
277 Catalysts. *Chem Rev*. 2020 Apr 22;120(8):3890–3938. doi: 10.1021/acs.chemrev.9b00662.
- 278 17. Su Y-H, Ke Y-F, Cai S-L, Yao Q-Y. Surface plasmon resonance of layer-by-layer gold
279 nanoparticles induced photoelectric current in environmentally-friendly plasmon-sensitized
280 solar cell. *Light Sci Appl* [Internet]. 2012 Jun 8;1(6):e14–e14. Available from:
281 <http://www.nature.com/articles/lsa201214>
- 282 18. Pérez-Tijerina E, Gracia Pinilla M, Mejía-Rosales S, Ortiz-Méndez U, Torres A, José-Yacamán
283 M. Highly size-controlled synthesis of Au/Pd nanoparticles by inert-gas condensation. *Faraday*
284 *Discuss* [Internet]. 2008;138:353–62. Available from: <http://xlink.rsc.org/?DOI=B705913M>
- 285 19. Sau TK, Murphy CJ. Seeded High Yield Synthesis of Short Au Nanorods in Aqueous Solution.
286 *Langmuir* [Internet]. 2004 Jul;20(15):6414–20. Available from:
287 <https://pubs.acs.org/doi/10.1021/la049463z>
- 288 20. Liu S, Chen G, Prasad PN, Swihart MT. Synthesis of Monodisperse Au, Ag, and Au–Ag Alloy
289 Nanoparticles with Tunable Size and Surface Plasmon Resonance Frequency. *Chem Mater*
290 [Internet]. 2011 Sep 27;23(18):4098–101. Available from:

- 291 <https://pubs.acs.org/doi/10.1021/cm201343k>
- 292 21. Ji X, Song X, Li J, Bai Y, Yang W, Peng X. Size Control of Gold Nanocrystals in Citrate
293 Reduction: The Third Role of Citrate. *J Am Chem Soc* [Internet]. 2007 Nov;129(45):13939–48.
294 Available from: <https://pubs.acs.org/doi/10.1021/ja074447k>
- 295 22. Kimling J, Maier M, Okenve B, Kotaidis V, Ballot H, Plech A. Turkevich Method for Gold
296 Nanoparticle Synthesis Revisited. *J Phys Chem B* [Internet]. 2006 Aug;110(32):15700–7.
297 Available from: <https://pubs.acs.org/doi/10.1021/jp061667w>
- 298 23. Ojea-Jiménez I, Bastús NG, Puentes V. Influence of the Sequence of the Reagents Addition in
299 the Citrate-Mediated Synthesis of Gold Nanoparticles. *J Phys Chem C* [Internet]. 2011 Aug
300 18;115(32):15752–7. Available from: <https://pubs.acs.org/doi/10.1021/jp2017242>
- 301 24. Sivaraman SK, Kumar S, Santhanam V. Monodisperse sub-10nm gold nanoparticles by
302 reversing the order of addition in Turkevich method – The role of chloroauric acid. *J Colloid*
303 *Interface Sci* [Internet]. 2011 Sep;361(2):543–7. Available from:
304 <https://linkinghub.elsevier.com/retrieve/pii/S0021979711007326>
- 305 25. Li C, Li D, Wan G, Xu J, Hou W. Facile synthesis of concentrated gold nanoparticles with low
306 size-distribution in water: temperature and pH controls. *Nanoscale Res Lett* [Internet]. 2011 Dec
307 6;6(1):440. Available from: [https://nanoscalereslett.springeropen.com/articles/10.1186/1556-](https://nanoscalereslett.springeropen.com/articles/10.1186/1556-276X-6-440)
308 [276X-6-440](https://nanoscalereslett.springeropen.com/articles/10.1186/1556-276X-6-440)
- 309 26. Zabetakis K, Ghann WE, Kumar S, Daniel M-C. Effect of high gold salt concentrations on the
310 size and polydispersity of gold nanoparticles prepared by an extended Turkevich–Frens method.
311 *Gold Bull* [Internet]. 2012 Dec 23;45(4):203–11. Available from:
312 <http://link.springer.com/10.1007/s13404-012-0069-2>
- 313 27. Raveendran P, Fu J, Wallen SL. A simple and “green” method for the synthesis of Au, Ag, and
314 Au–Ag alloy nanoparticles. *Green Chem* [Internet]. 2006;8(1):34–8. Available from:
315 <http://xlink.rsc.org/?DOI=B512540E>
- 316 28. Liu Y-C, Lin L-H, Chiu W-H. Size-Controlled Synthesis of Gold Nanoparticles from Bulk Gold
317 Substrates by Sonoelectrochemical Methods. *J Phys Chem B* [Internet]. 2004
318 Dec;108(50):19237–40. Available from: <https://pubs.acs.org/doi/10.1021/jp046866z>
- 319 29. Huang X, Qi X, Huang Y, Li S, Xue C, Gan CL, et al. Photochemically Controlled Synthesis of
320 Anisotropic Au Nanostructures: Platelet-like Au Nanorods and Six-Star Au Nanoparticles. *ACS*
321 *Nano* [Internet]. 2010 Oct 26;4(10):6196–202. Available from:
322 <https://pubs.acs.org/doi/10.1021/nn101803m>
- 323 30. Zhao W, Lee TMH, Leung SSY, Hsing I-M. Tunable Stabilization of Gold Nanoparticles in
324 Aqueous Solutions by Mononucleotides. *Langmuir* [Internet]. 2007 Jun;23(13):7143–7.
325 Available from: <https://pubs.acs.org/doi/10.1021/la7006843>
- 326 31. Obliosca JM, Arellano IHJ, Huang MH, Arco SD. Double layer micellar stabilization of gold
327 nanocrystals by greener ionic liquid 1-butyl-3-methylimidazolium lauryl sulfate. *Mater Lett*
328 [Internet]. 2010 May;64(9):1109–12. Available from:
329 <https://linkinghub.elsevier.com/retrieve/pii/S0167577X10001503>
- 330 32. Dash P, Scott RWJ. 1-Methylimidazole stabilization of gold nanoparticles in imidazolium ionic
331 liquids. *Chem Commun* [Internet]. 2009;(7):812. Available from:
332 <http://xlink.rsc.org/?DOI=b816446k>
- 333 33. Orthaber A, Löfås H, Öberg E, Grigoriev A, Wallner A, Jafri SHM, et al. Cooperative Gold
334 Nanoparticle Stabilization by Acetylenic Phosphaalkenes. *Angew Chemie Int Ed* [Internet].
335 2015 Sep 1;54(36):10634–8. Available from:
336 <https://onlinelibrary.wiley.com/doi/10.1002/anie.201504834>
- 337 34. Blinov AV, Gvozdenko AA, Kravtsov AA, Krandievsky SO, Blinova AA, Maglakelidze DG, et
338 al. Synthesis of nanosized manganese methahydroxide stabilized by cystine. *Mater Chem Phys*
339 [Internet]. 2021 Jun;265(December 2020):124510. Available from:
340 <https://doi.org/10.1016/j.matchemphys.2021.124510>
- 341 35. Blinov A V., Kravtsov AA, Krandievskii SO, Timchenko VP, Gvozdenko AA, Blinova AA.
342 Synthesis of MnO₂ Nanoparticles Stabilized by Methionine. *Russ J Gen Chem*.
343 2020;90(2):283–6.

- 344 36. Blinov AV, Yasnaya MA, Blinova AA, Shevchenko IM, Momot EV, Gvozdenko AA, et al.
345 COMPUTER QUANTUM-CHEMICAL SIMULATION OF POLYMERIC STABILIZATION
346 OF SILVER NANOPARTICLES. *Phys Chem Asp study Clust nanostructures Nanomater*
347 [Internet]. 2019 Dec 16;(11):414–21. Available from: <https://physchemaspects.ru/2019/doi-10-26456-pcascnn-2019-11-414/?lang=en>
348
- 349 37. Siddiqui SA, Blinov AV, Serov AV, Gvozdenko AA, Kravtsov AA, Nagdalian AA, Raffa VV,
350 Maglakelidze DG, Blinova AA, Kobina AV, et al. Effect of Selenium Nanoparticles on
351 Germination of Hordéum Vulgáre Barley Seeds. *Coatings* 2021, 11, 862
- 352 38. Boisselier E, Diallo AK, Salmon L, Ornelas C, Ruiz J, Astruc D. Encapsulation and
353 Stabilization of Gold Nanoparticles with “Click” Polyethyleneglycol Dendrimers. *J Am Chem*
354 *Soc* [Internet]. 2010 Mar 3;132(8):2729–42. Available from:
355 <https://pubs.acs.org/doi/10.1021/ja909133f>
- 356 39. Li N, Echeverría M, Moya S, Ruiz J, Astruc D. “Click” Synthesis of Nona-PEG-branched
357 Triazole Dendrimers and Stabilization of Gold Nanoparticles That Efficiently Catalyze p -
358 Nitrophenol Reduction. *Inorg Chem* [Internet]. 2014 Jul 7;53(13):6954–61. Available from:
359 <https://pubs.acs.org/doi/10.1021/ic500861f>
- 360 40. Franconetti A, Carnerero JM, Prado-Gotor R, Cabrera-Escribano F, Jaime C. Chitosan as a
361 capping agent: Insights on the stabilization of gold nanoparticles. *Carbohydr Polym* [Internet].
362 2019 Mar;207:806–14. Available from:
363 <https://linkinghub.elsevier.com/retrieve/pii/S0144861718314929>
- 364 41. Leiva A, Bonard S, Pino M, Saldías C, Kortaberria G, Radić D. Improving the performance of
365 chitosan in the synthesis and stabilization of gold nanoparticles. *Eur Polym J*. 2015;
- 366 42. Tiwari AD, Mishra AK, Mishra SB, Arotiba OA, Mamba BB. Green synthesis and stabilization
367 of gold nanoparticles in chemically modified chitosan matrices. *Int J Biol Macromol* [Internet].
368 2011 May;48(4):682–7. Available from:
369 <https://linkinghub.elsevier.com/retrieve/pii/S0141813011000614>
- 370 43. Matei I, Buta CM, Turcu IM, Culita D, Munteanu C, Ionita G. Formation and Stabilization of
371 Gold Nanoparticles in Bovine Serum Albumin Solution. *Molecules* [Internet]. 2019 Sep
372 18;24(18):3395. Available from: <https://www.mdpi.com/1420-3049/24/18/3395>
- 373 44. Yasmin A, Ramesh K, Rajeshkumar S. Optimization and stabilization of gold nanoparticles by
374 using herbal plant extract with microwave heating. *Nano Converge* [Internet]. 2014 Dec
375 11;1(1):12. Available from: <http://www.nanoconvergencejournal.com/content/1/1/12>
- 376 45. Jia X, Xu X, Zhang L. Synthesis and Stabilization of Gold Nanoparticles Induced by
377 Denaturation and Renaturation of Triple Helical β -Glucan in Water. *Biomacromolecules*
378 [Internet]. 2013 Jun 10;14(6):1787–94. Available from:
379 <https://pubs.acs.org/doi/10.1021/bm400182q>
- 380 46. Yasnaya M.A., Blinov A.V., Blinova A.A., Shevchenko I.M., Maglakelidze D.G., Senkova
381 A.V. DETERMINATION OF OPTIMAL MODES FOR MEASURING THE SIZE OF
382 COLLOIDAL PARTICLES BY PHOTON-CORRELATION SPECTROSCOPY AND
383 ACOUSTIC SPECTROSCOPY. *Phys Chem Asp Study Clust Nanostructures Nanomater*. 2020
384 Dec;(12(1)):232–42.
- 385 47. Blinov AV, Kravtsov AA, Raffa VV, Kramarenko VN, Krandievsky SO, Maglakelidze DG, et
386 al. INFLUENCE OF SYNTHESIS CONDITIONS ON AGGREGATIVE STABILITY OF Ag
387 ALCOSOLS. *Phys Chem Asp Study Clust Nanostructures Nanomater* [Internet]. 2020 Dec
388 15;(12(1)):25–32. Available from: <https://physchemaspects.ru/2020/doi-10-26456-pcascnn-2020-12-025>
389
390